

Crystal Growth: Physics, Technology and Modeling

Stanisław Krukowski & Michał Leszczyński
Institute of High Pressure Physics PAS
01-142 Warsaw, Sokołowska 29/37
e-mail: stach@unipress.waw.pl, mike@unipress.waw.pl

Zbigniew Żytkiewicz
Institute of Physics PAS
02-668 Warsaw, Al. Lotników 32/46
E-mail: zytkie@ifpan.edu.pl


Lecture 7. Step motion

<http://www.unipress.waw.pl/~stach/cg-2021-22>

Scope

- **Vicinal surface - step trains**
- **Step meandering**
- **Step bunching**
- **Double steps**
- **Macro steps**
- **Mounds & Islands**

Vicinal surface – step trains


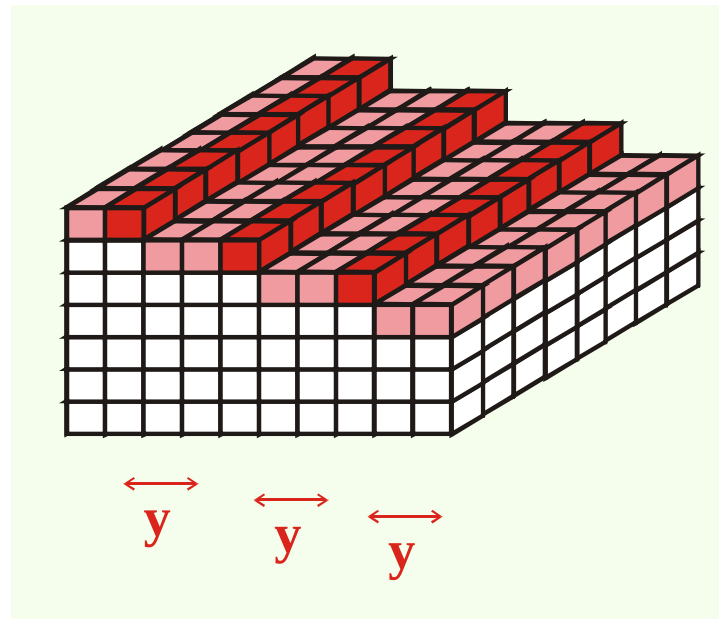


Misorientation

$$a = y \operatorname{tg}(\alpha) \quad \longrightarrow \quad \alpha = \operatorname{atan}\left(\frac{a}{y}\right)$$

Step instabilities - meandering

- Si(111) surface deposition

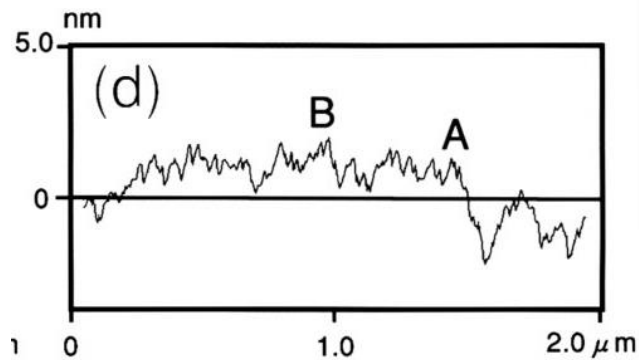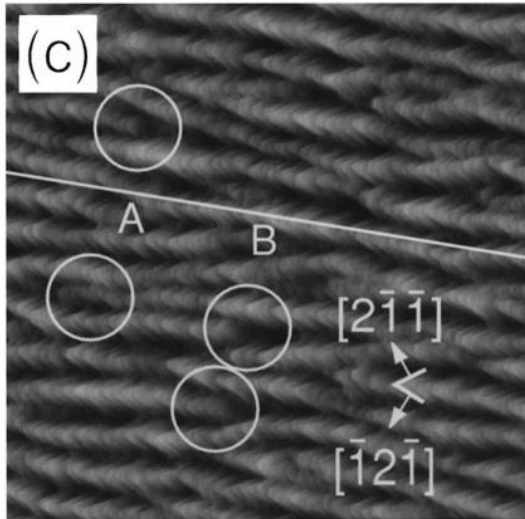

*H. Omi, T. Ogino, Thin Solid Films
380 (2000) 15*

- GaN(0001) - MOVPE



AFM – G. Nowak

*S. Krukowski et al. Cryst. Res. Technol.
42 (2007) 1281*

Step fluctuations - equilibrium

- **Drumhead – elastic model**

$$F = \int dx \left[\frac{G}{2} \left(\frac{\partial z}{\partial x} \right)^2 + U z^2 \right] = \sum_k \left[\frac{G k^2}{2} + U \right] z_k^2$$



z – deviation from the straight line (z = 0)

- **Average width**

$$\langle z^2 \rangle = \frac{\int dz z^2 \exp(-F/kT)}{\int dz \exp(-F/kT)} \cong \int \frac{2\pi k}{G k^2 + 2U} dk$$

$$\langle z^2 \rangle \cong \pi \ln \left(\frac{G}{2} \left(\frac{\pi}{2L} \right)^2 + U \right) = \lim_{L \rightarrow \infty, U \rightarrow 0} 2 \ln(L) = \infty$$


Step fluctuations - Monte Carlo equilibrium simulations

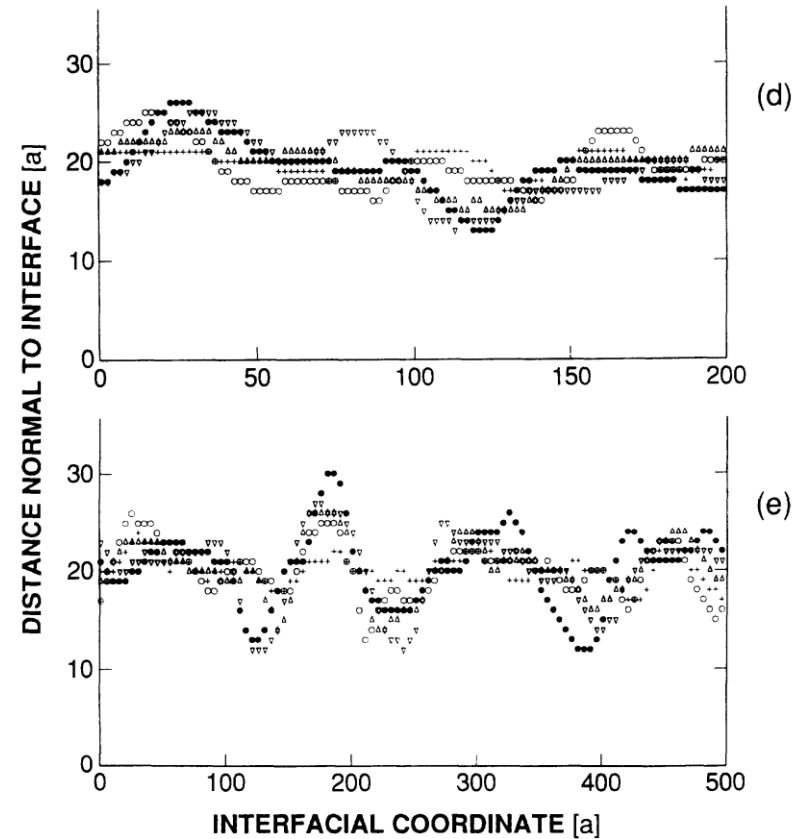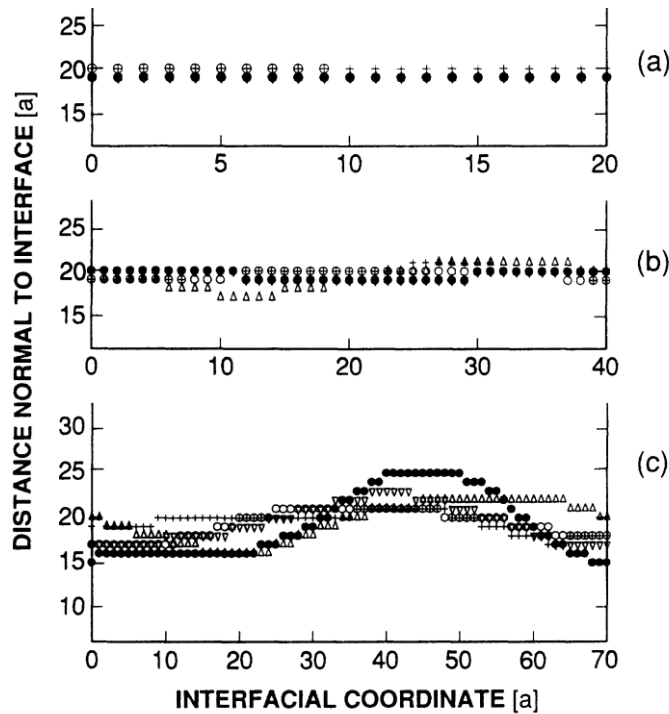


**S. Krukowski, F. Rosenberger,
Phys. Rev. B 49 (1994) 12 464**

Step meandering mechanism

- **Ehrlich-Schwoebel effect**

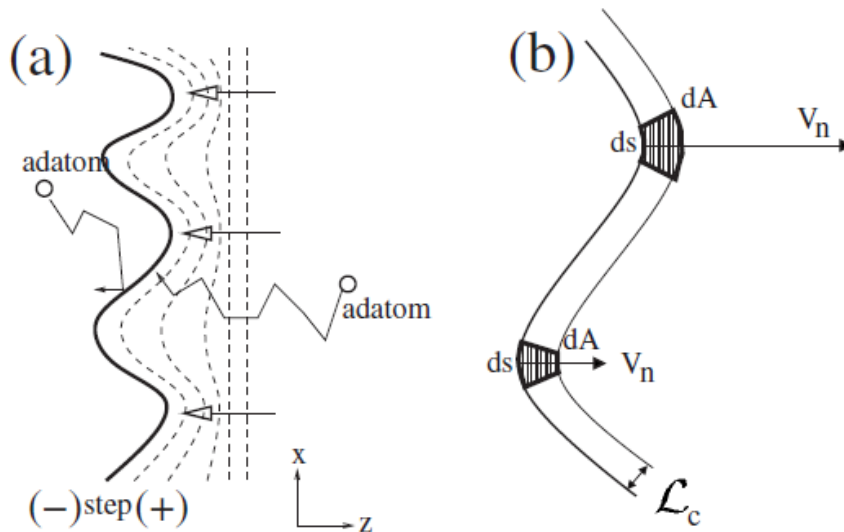

- **K-S instability**

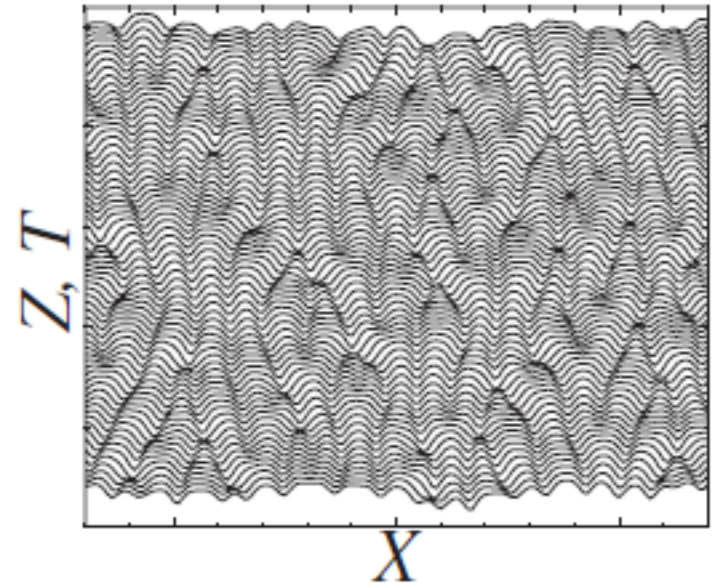


C. Misbah, O. Pierre-Luis, Y. Saito Rev. Mod. Phys. 82(2010) 981

Step fluctuations in nonequilibrium - Kuramoto-Sivashinski equation

- Deviation from straight step - $\zeta = \zeta(x, t)$ in BCF solution



$$\frac{\partial \zeta}{\partial t} = -a \frac{\partial^2 \zeta}{\partial x^2} - b \frac{\partial^4 \zeta}{\partial x^4} + v \left(\frac{\partial \zeta}{\partial x} \right)^2$$

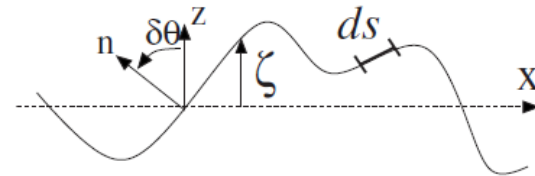

Lyapunov stability

$$\zeta = \zeta_0 \exp(\lambda t - ikx) \quad \lambda = ak^2 - bk^4 + f(k) = \begin{cases} > 0 & \text{unstable} \\ < 0 & \text{stable} \end{cases}$$

**Broken
parity
travelling
mode**

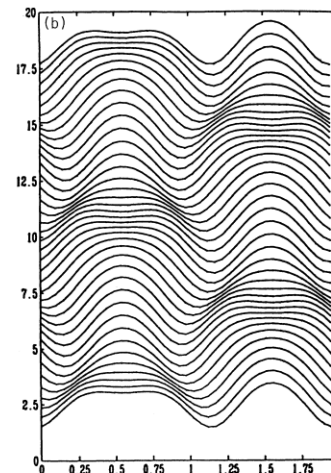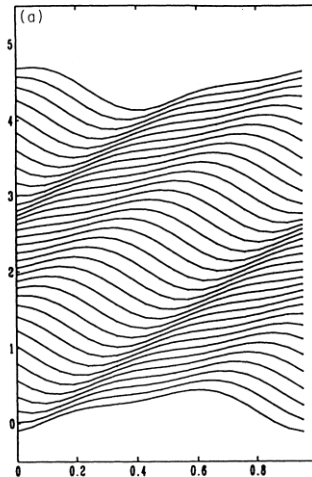


**Vacillating-
breathing
mode**

Step fluctuations in nonequilibrium – Kardar-Parisi-Zhang (KPZ) equation

- Deviation from straight step - $h = h(x, t)$

$$\frac{\partial h}{\partial t} = v \frac{\partial^2 h}{\partial x^2} + \frac{\lambda}{2} \left(\frac{\partial h}{\partial x} \right)^2 + \eta(x, t)$$

$\eta(x, t)$ - random force



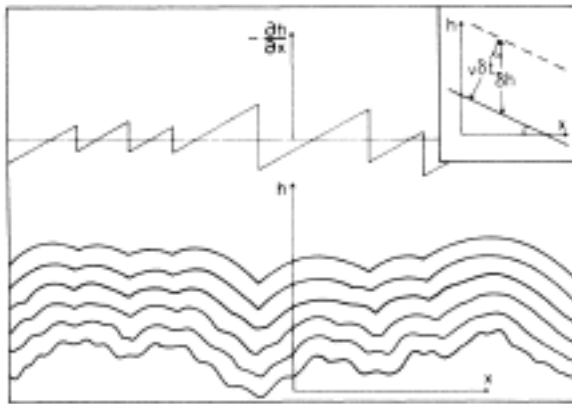


Successive profiles obtained from KPZ equation

Inset – perpendicular growth mechanism



M. Kardar, G. Parisi, Y-C. Zhang
Phys. Rev. Lett. 56 (1986) 889

Step difference related meandering mechanism

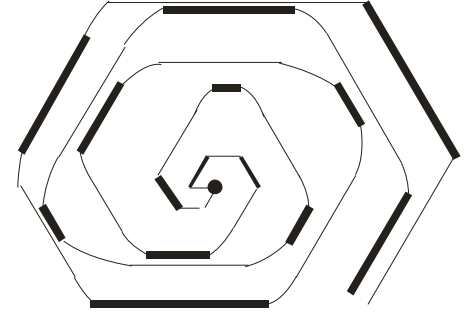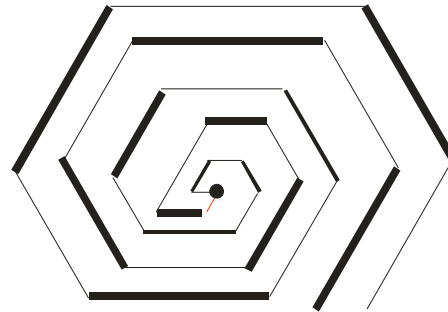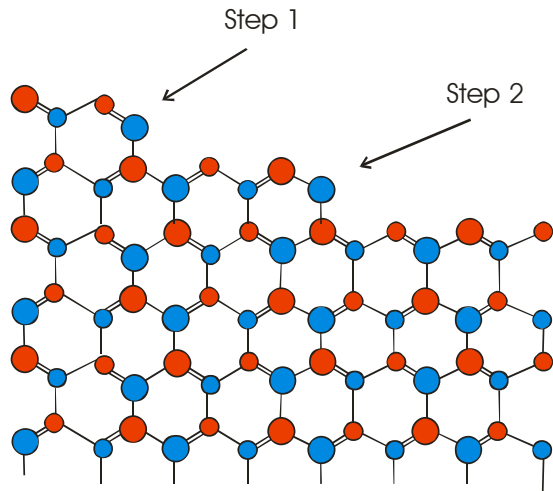


Monte Carlo simulation of surface diffusion – GaN(0001) surface

- Step structures

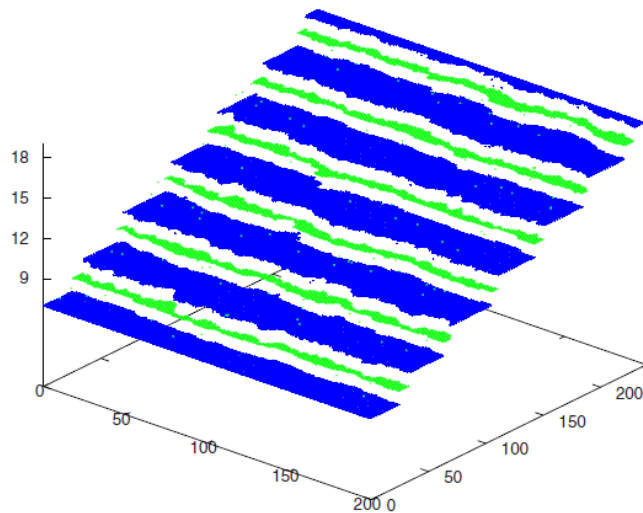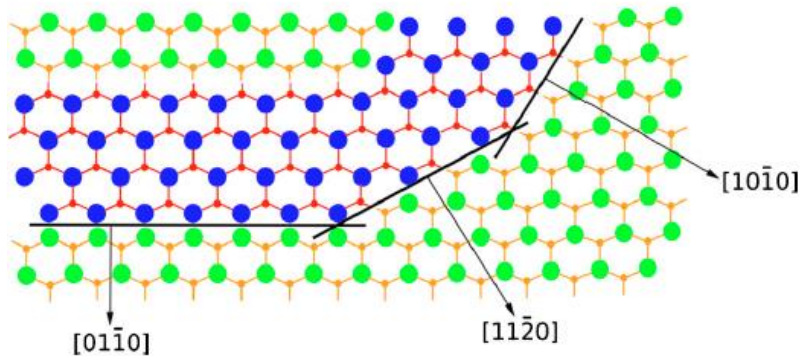

- Ehrlich-Schwoebel effect - E_{bar}

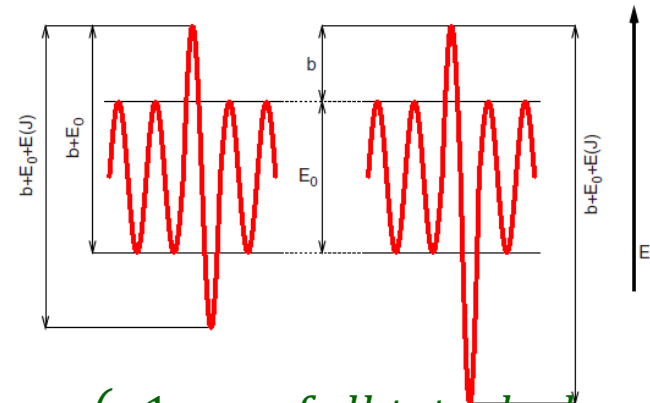

$$\alpha = \begin{cases} 1 & \text{full tetrahedron} \\ \frac{1}{3}rn & \text{not full tetrahedron} \end{cases}$$

$$E = \phi \sum_{i=1}^4 \alpha_i$$

$$P = v \exp\left(-\frac{\Delta E + E_{bar}}{kT}\right)$$

M. Załuska-Kotur et al.


J. Appl. Phys. 109 (2011) 023515

23.11.2021 – Step motion

MC simulation – GaN(0001) surface – difference in dynamics

$r = 0.4$

$r = 1$

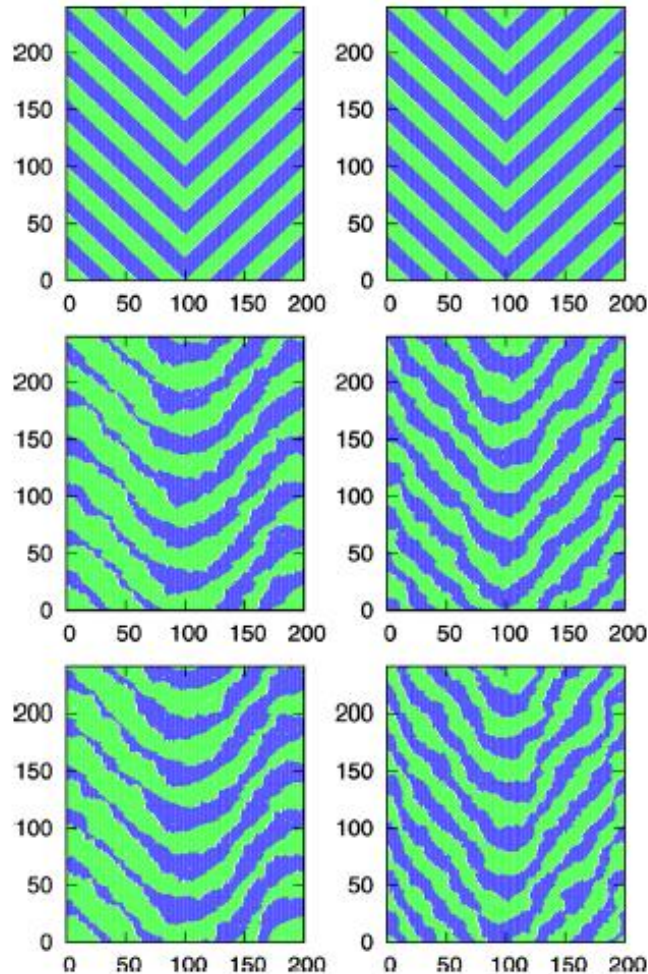

$t = 0$ MC steps

$t = 5 \times 10^6$ MC steps


$t = 1 \times 10^7$ MC steps

M. Załuska-Kotur et al.



J. Appl. Phys. 109 (2011) 023515

23.11.2021 – Step motion

MOVPE growth and MC simulations of GaN(0001) surface

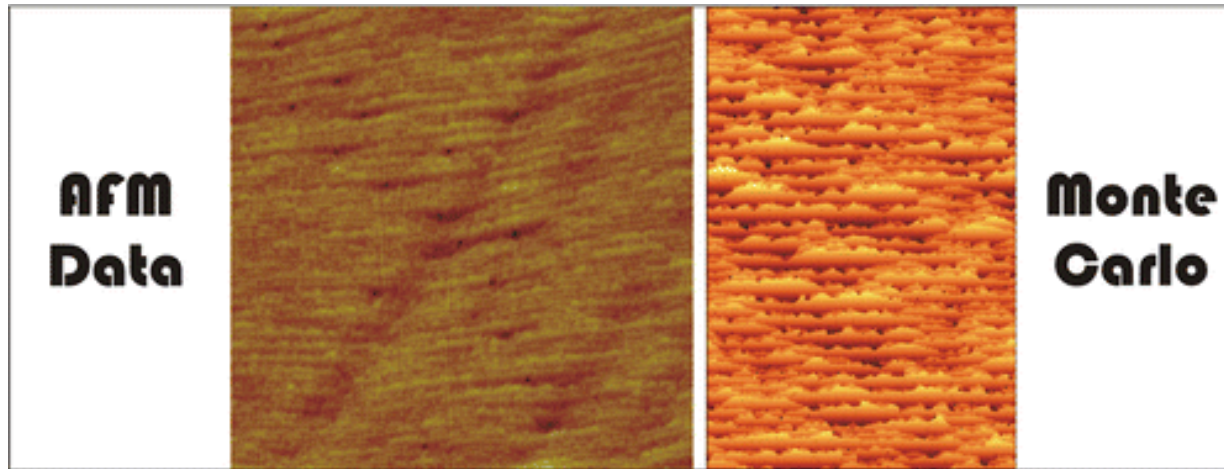




*M. Załuska-Kotur et al.
Cryst. Growth Des.
13 (2013) 1006*

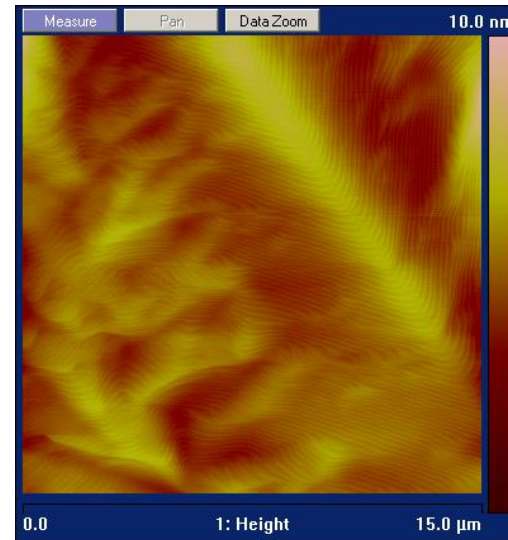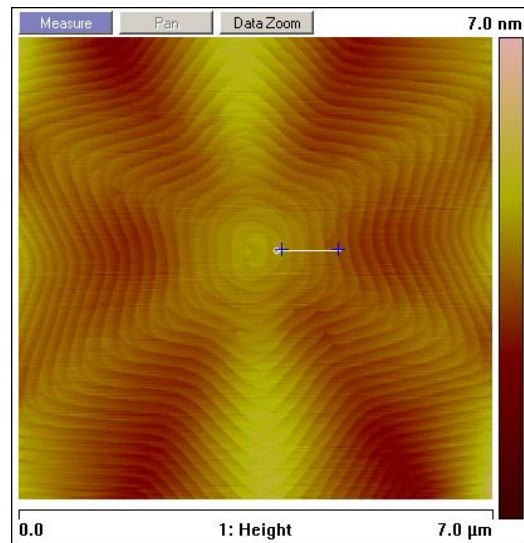


R. Czernecki, AFM data

Step bunching

- Ehrlich-Schwoebel effect

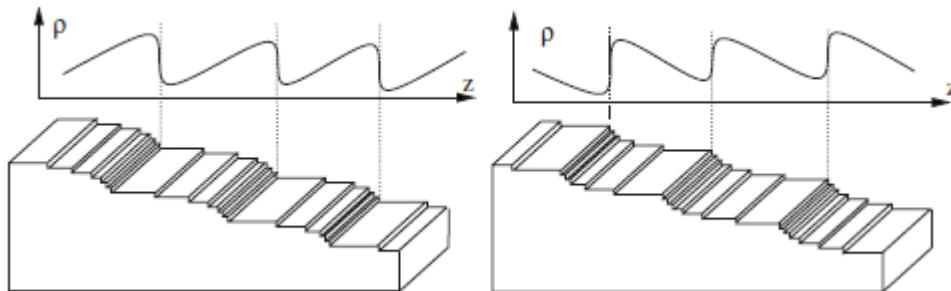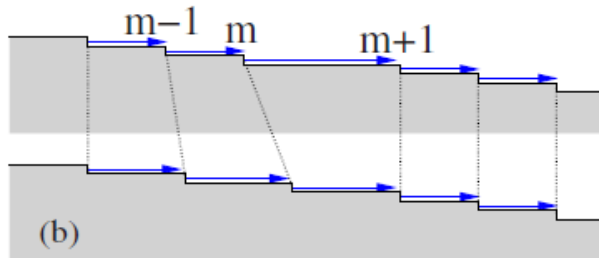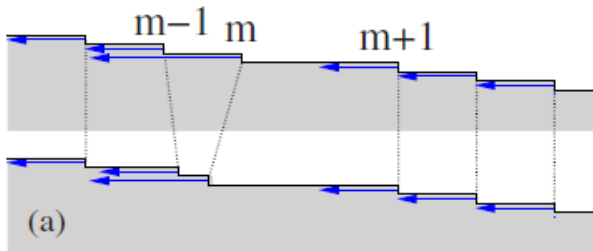


Step bunching – Si growth – instability mechanism

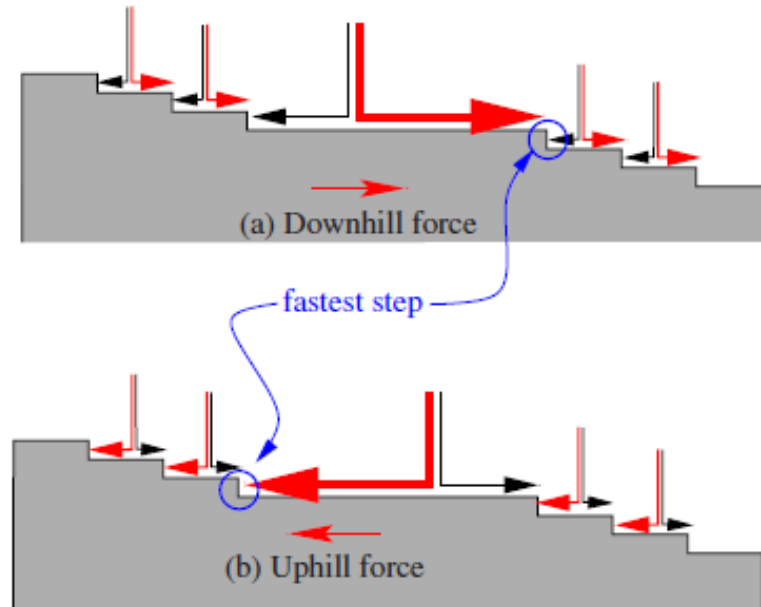


*C. Misbah, O. Pierre-Luis, Y. Saito,
Rev. Mod. Phys. 82(2010) 981*

Si growth – double steps

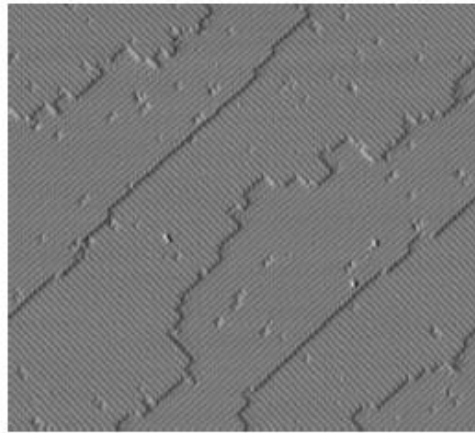

(a)

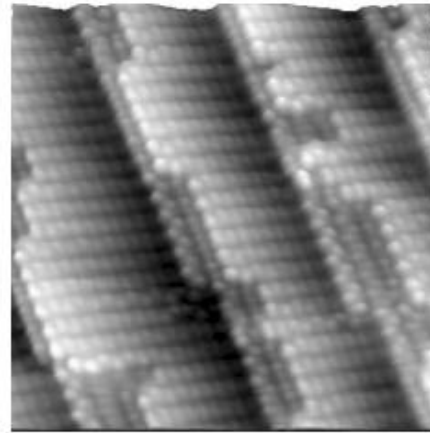


(b)

- **AFM – M. Lagally**




*C. Misbah, O. Pierre-Luis, Y. Saito,
Rev. Mod. Phys. 82(2010) 981*

Step bunching – Si growth

- Macrosteps
- Single steps on terraces

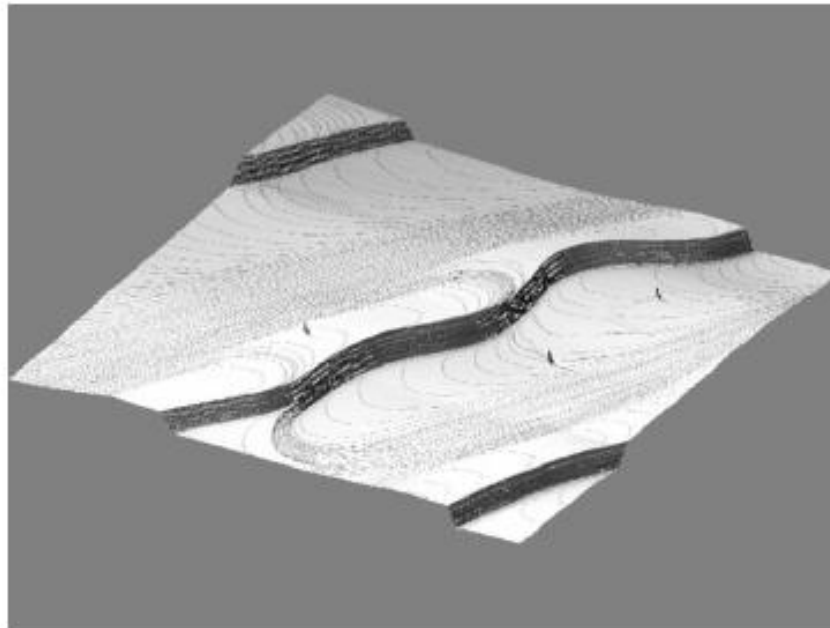

Si(111) surface - annealing

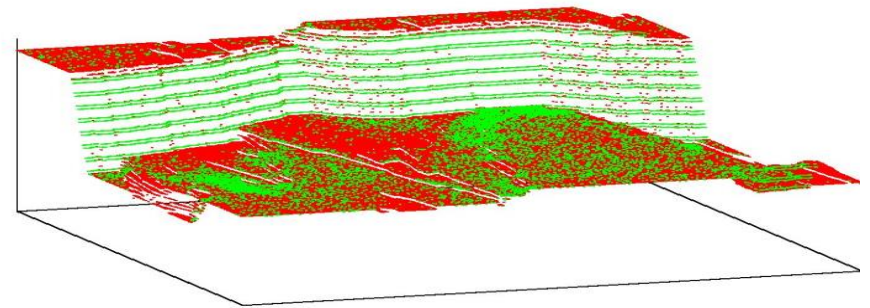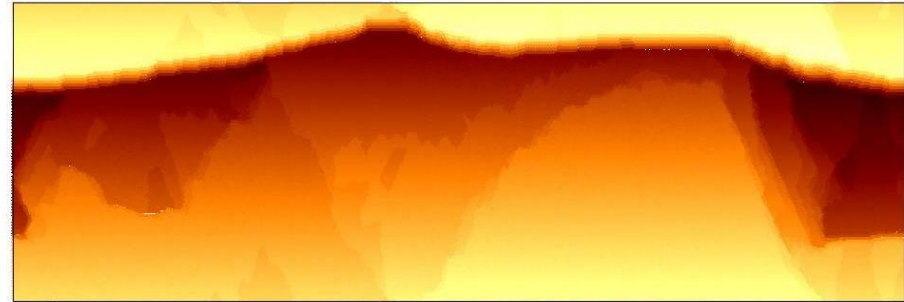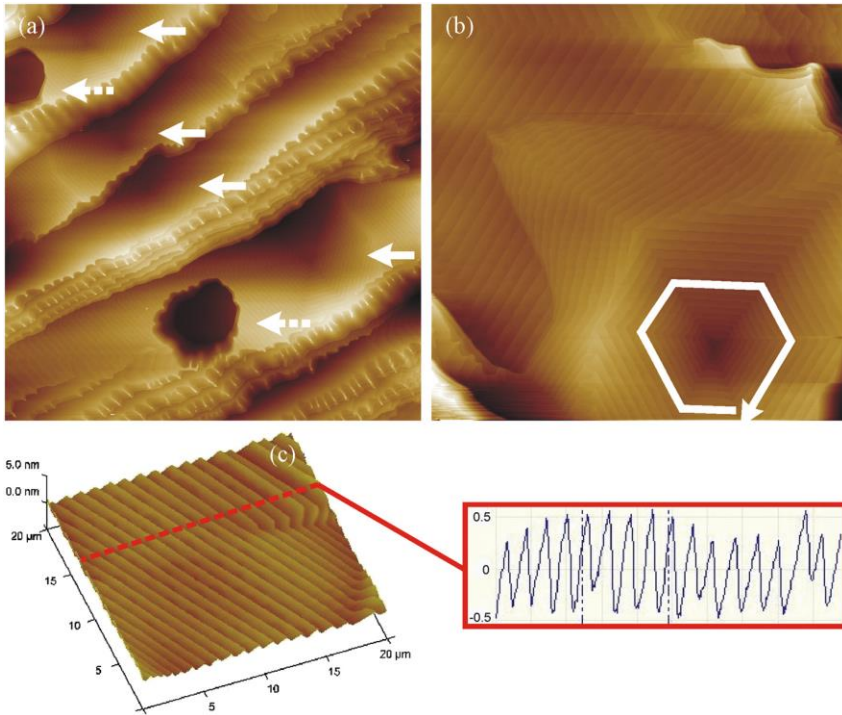

J. Hassan et al., J. Cryst. Growth 310 (2008) 4430

2-d nucleation on terraces – Pt on Pt(111)

0.3 ML

3 ML

12 ML

90 ML


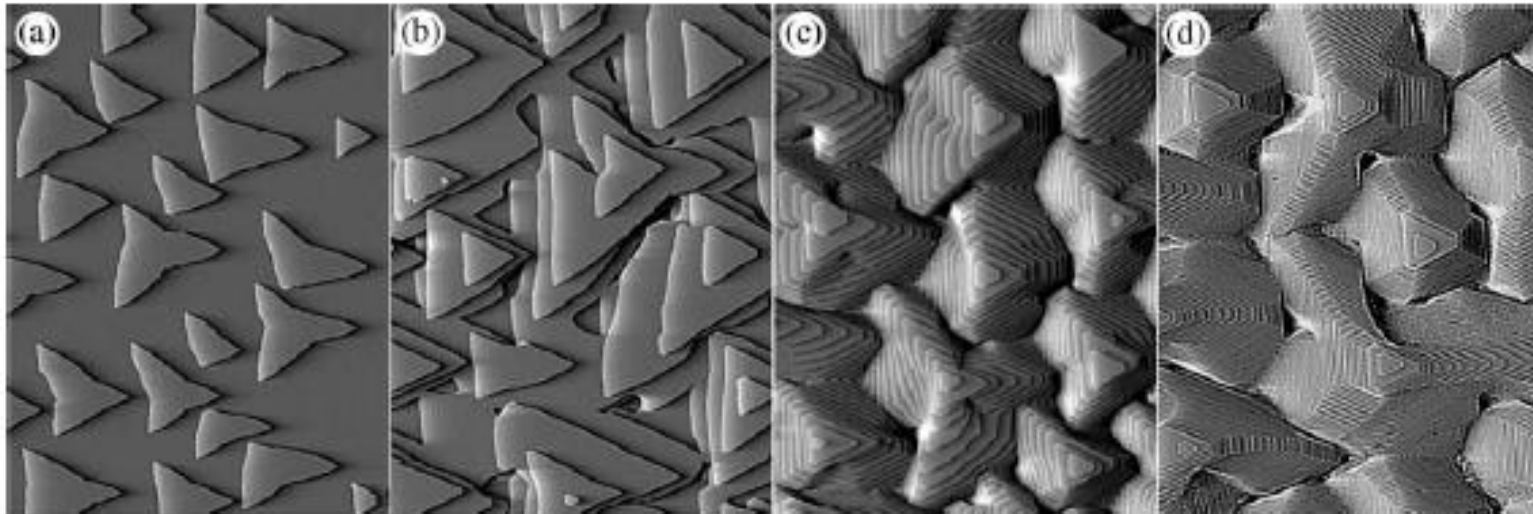


Fig. 2. Growth of Pt on Pt(111) at $T=440$ K [5]. The total coverage is (a) 0.3 monolayers (ML), (b) 3 ML, (c) 12 ML and (d) 90 ML. The image size is $2600 \text{ \AA} \times 3450 \text{ \AA}$. Courtesy of T. Michely.

J. Krug, *Physica A* 313 (2002) 47


2-d nucleation on terraces – GaN on GaN (0001)

MC simulation

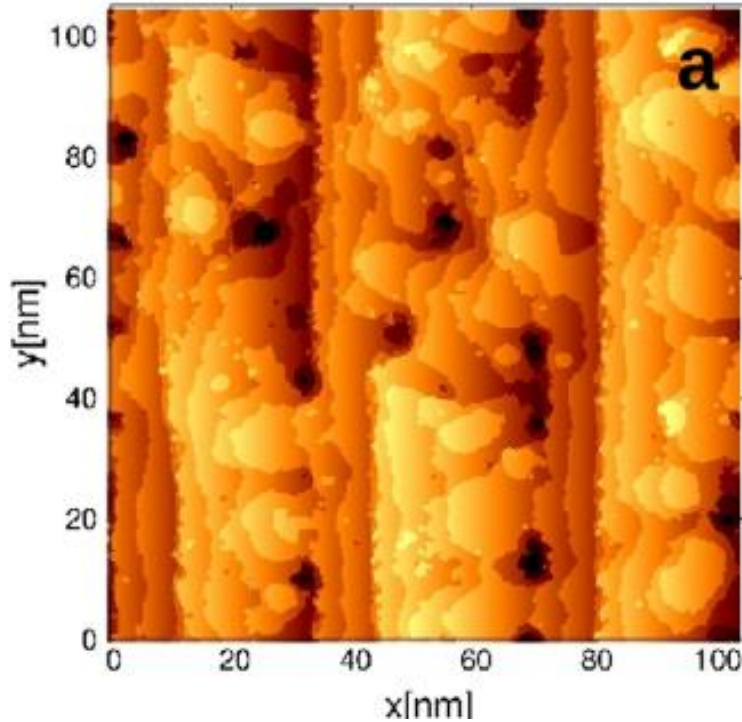

$\alpha = 2 \text{ arc deg}$

MBE growth

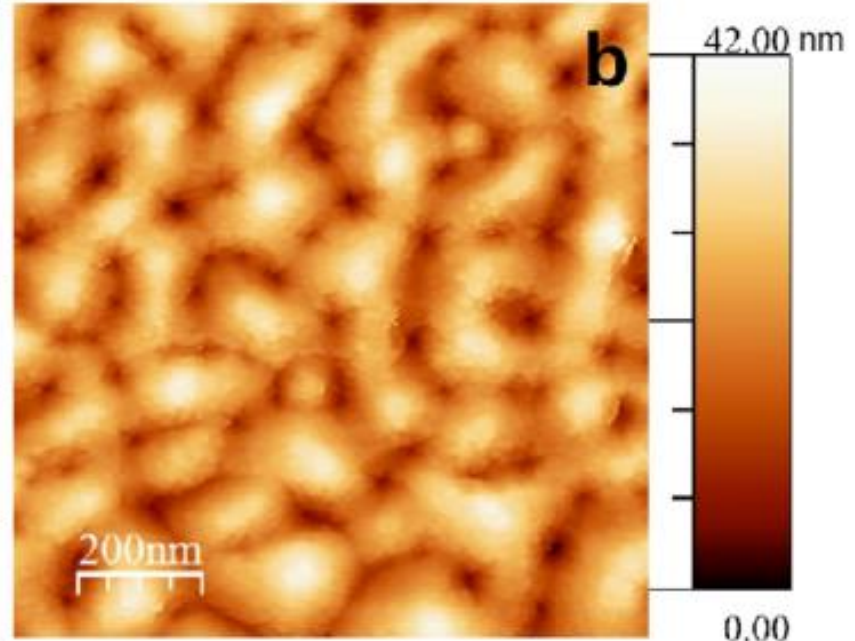


$T = 750 \text{ }^{\circ}\text{C}$

F. Krzyzewski et al., J. Cryst. Growth 457 (2017) 38


2-d nucleation on terraces – GaN on GaN (0001)

MC simulation

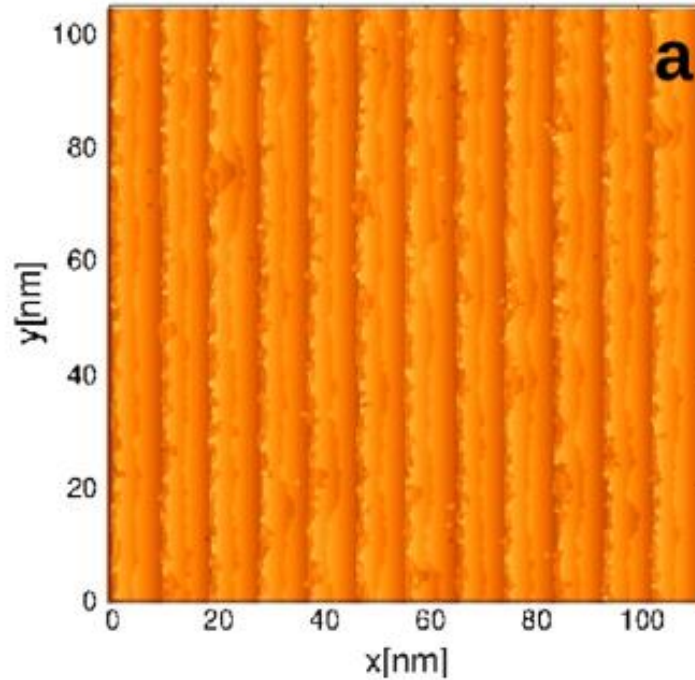

$\alpha = 4 \text{ arc deg}$

MBE growth

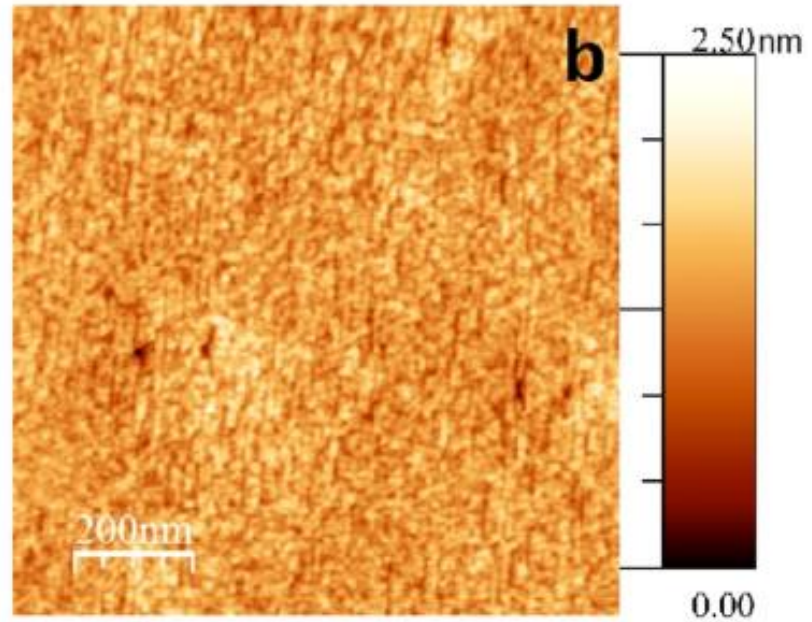


$T = 750 \text{ }^{\circ}\text{C}$

F. Krzyzewski et al., J. Cryst. Growth 457 (2017) 38


Subsequent layers - mounds

AFM image of a nonideal synthetic dolomite from the Mg:Ca = 1.0 experiment showing mound nanotopography.

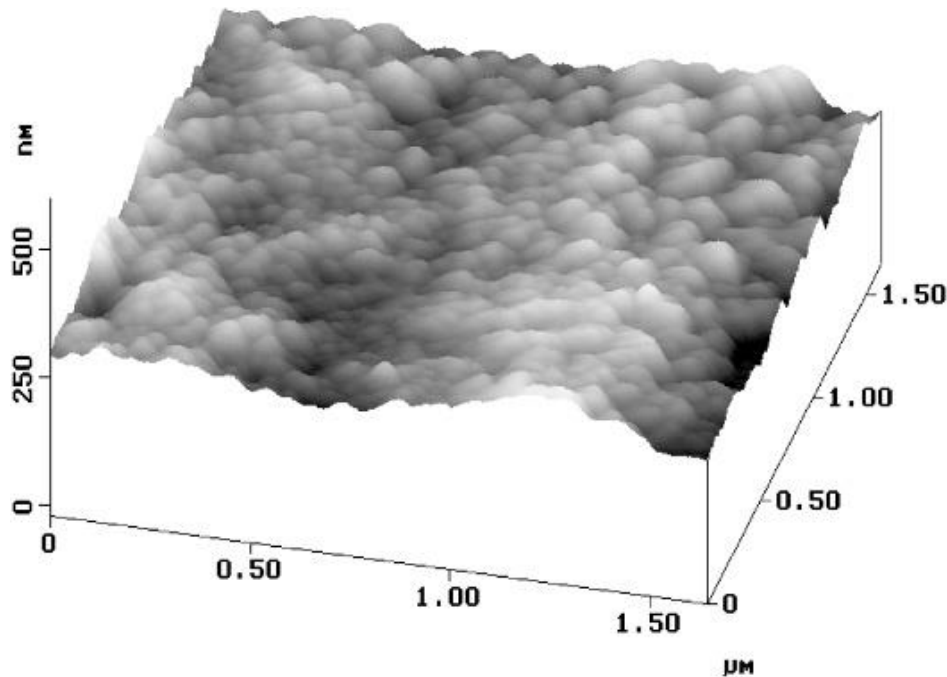


**S.E. Kaczmarek & D.F. Sibley,
Journal of Sedimentary Research, 77 (2007) 424**


Surface – flux connection

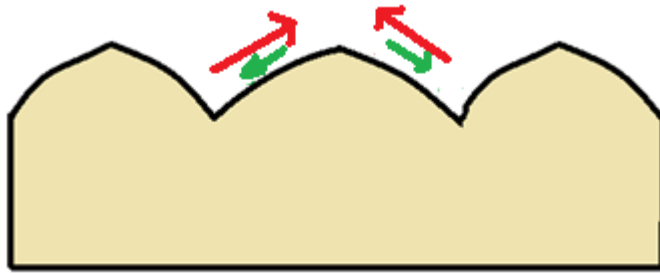

Unstable – growth of the mounds

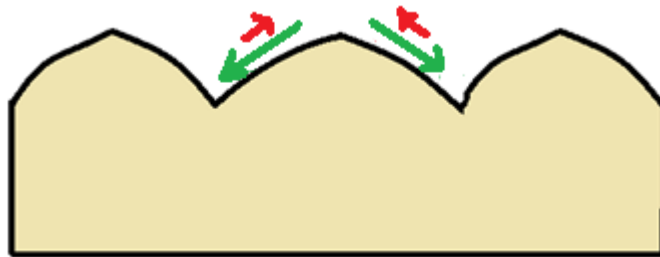

Stable flat surface – mounds disappearing

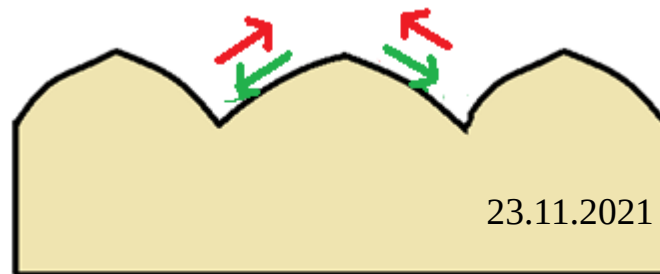


Stable mounds

Surface dynamics – mounds growth

- Flat surface growth :


Mounds growth – monostep motion

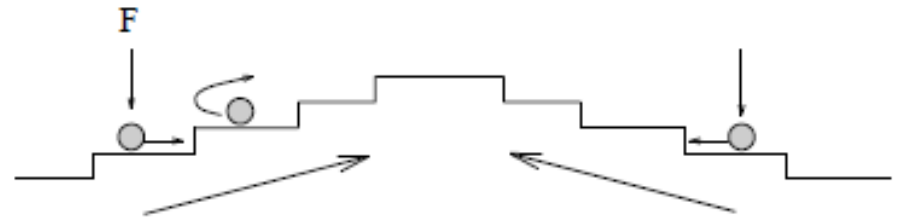

$$\frac{d\theta_n}{dt} = F (\theta_{n-1} - \theta_n)$$

$$\theta_n = 1 - e^{-\Theta} \sum_{j=0}^{n-1} \frac{\Theta^j}{j!}$$

$$\Theta = \sum_{j=0}^{\infty} \theta_j = Ft$$

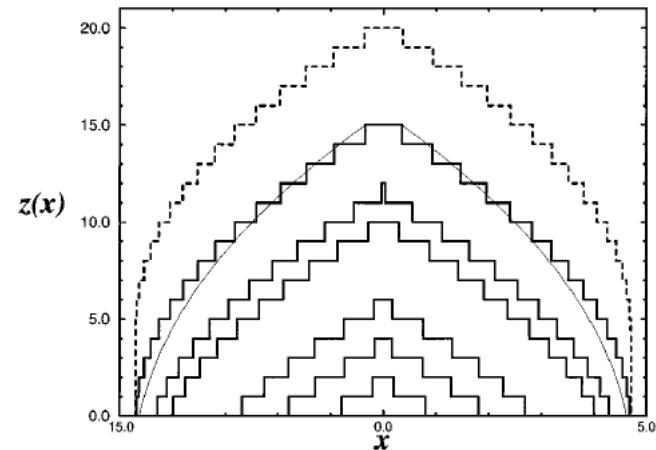

**P. Politi & J. Villain,
Phys. Rev. B 54 (1996) 5114**

Literature

- ***H. Omi, T. Ogino, Thin Solid Films 380 (2000) 15***
- ***S. Krukowski, & F. Rosenberger, Phys. Rev. B 49 (1994) 12 464***
- ***I. Bena, C. Misbah, A. Valence, Phys. Rev. B 47 (1993) 7408***
- ***M. Kardar, G. Parisi, Y-C. Zhang, Phys. Rev. Lett. 56 (1986) 889***
- ***S. Krukowski, et al., Cryst. Res. Technol. 42 (2007) 1281***
- ***M. Załuska-Kotur et al., J. Appl. Phys. 109 (2011) 023515***
- ***M. Załuska-Kotur et al., Cryst. Growth Des. 13 (2013) 1006***
- ***C. Misbah, O. Pierre-Luis, Y. Saito, Rev. Mod. Phys. 82(2010) 981***
- ***J. Hassan et al., J. Cryst. Growth 310 (2008) 4430***
- ***J. Krug, Physica A 313 (2002) 47***
- ***F. Krzyzewski et al., J. Cryst. Growth 457 (2017) 38***
- ***S.E. Kaczmarek & D.F. Sibley, Journal of Sedimentary Research, 77 (2007) 424***
- ***P. Politi & J. Villain, Phys. Rev. B 54 (1996) 5114***